

SL-61MAG

FLUX CORED ARC WELDING CONSUMABLE
FOR WELDING OF MILD STEEL



❖ Specification

<i>AWS A5.20</i>	E61T-GM
<i>(AWS A5.20M)</i>	E431T-GM)
<i>EN ISO17632-A</i>	T38 2 P M21 1 H5
<i>EN ISO17632-B</i>	T43 2 T1 1 M A H5

❖ Applications

All position welding of shipbuilding, steel construction, bridges, offshore, pipes, and pressure vessels.

❖ Characteristics on Usage

SL-61MAG is titania type Seamless Flux Cored Wire applicable for all position welding with Ar + 20~25%CO₂ shielding gas. SL-61MAG offer optimal protection against moisture reabsorption. During use, moisture cannot penetrate into the filling since there is no closed seam running over the wire length. This extremely low level of diffusible hydrogen prevents the weld from hydrogen induced cracking or cold cracking.

❖ Note on Usage


1. Proper preheating(50~150°C, 122~302°F) and interpass temperature must be used in order to release hydrogen which may cause cracking in weld metal when electrodes are used for medium and heavy plates.
2. Use Ar+20~25%CO₂ gas.



Mechanical Properties & Chemical Composition of All Weld Metal

❖ Welding Conditions

Method by AWS Spec.

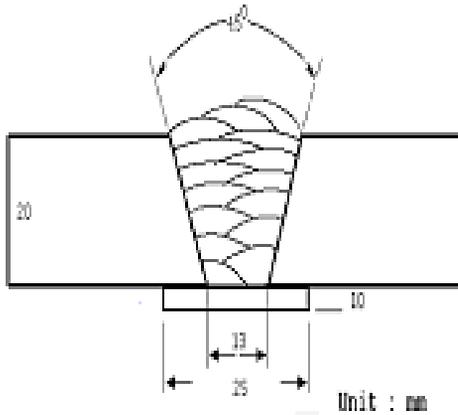

[Joint Preparation & Layer Details]

Welding Position	: 1G(PA)
Diameter	: 1.2mm (0.045in)
Shielding Gas	: Ar+20%CO ₂
Flow Rate	: 20 ℓ /min
Amp / Volt	: 270~280A / 29~30V
Stick-Out	: 20~25mm (0.79~0.98in)
Pre-Heat	: R.T .
Interpass Temp.	: 150±15℃ (302±59°F)
Polarity	: DC(+)

❖ Mechanical Properties of all weld metal

Consumable	Tensile Test			CVN Impact Test J(ft · lbs)
	YS MPa (lbs/in ²)	TS MPa (lbs/in ²)	EL (%)	-18℃ (0°F)
SL-61MAG	524(76,000)	577(83,700)	29.0	89(66)
AWS A5.20 E61T-GM	≥ 330 (48,000)	430~600 (60,000~80,000)	≥ 22	-

❖ Chemical Analysis of all weld metal(wt%)

Consumable	C	Si	Mn	P	S
SL-61MAG	0.031	0.22	1.54	0.013	0.005
AWS A5.20 E61T-GM	-	-	-	-	-


This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



Mechanical Properties & Chemical Composition of All Weld Metal

❖ Welding Conditions

Method by AWS Spec.

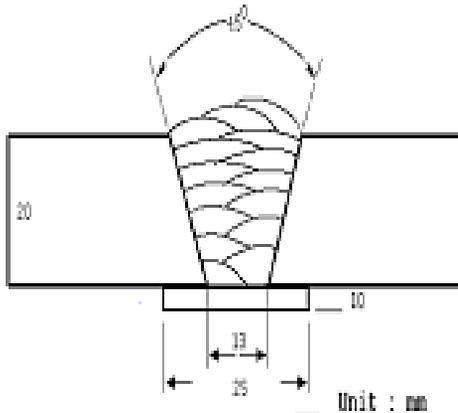

[Joint Preparation & Layer Details]

Welding Position	: 1G(PA)
Diameter	: 1.6mm (1/16in)
Shielding Gas	: Ar+20%CO ₂
Flow Rate	: 20 ℓ /min
Amp / Volt	: 320~330A / 29~30V
Stick-Out	: 20~25mm (0.79~0.98in)
Pre-Heat	: R.T .
Interpass Temp.	: 150±15℃ (302±59°F)
Polarity	: DC(+)

❖ Mechanical Properties of all weld metal

Consumable	Tensile Test			CVN Impact Test J(ft · lbs)
	YS MPa (lbs/in ²)	TS MPa (lbs/in ²)	EL (%)	-18℃ (0°F)
SL-61MAG	491(71,200)	555(80,500)	29.8	73(54)
AWS A5.20 E61T-GM	≥ 330 (48,000)	430~600 (60,000~80,000)	≥ 22	-

❖ Chemical Analysis of all weld metal(wt%)

Consumable	C	Si	Mn	P	S
SL-61MAG	0.028	0.20	1.48	0.013	0.005
AWS A5.20 E61T-GM	-	-	-	-	-

This information is provided solely for the purpose of confirming product conformance with applicable standards. The serviceability of a product or structure utilizing this type of information is and must be the sole responsibility of the builder/user. Many variables beyond the control of HYUNDAI WELDING CO., LTD. affect the results obtained in applying this type of information. These variables include, but are not limited to, welding procedure, shielding gas, plate chemistry and temperature, weldment design, fabrication methods and service requirements.



Diffusible Hydrogen Content

❖ Welding Conditions

Diameter	: 1.2mm (0.045in)	Amps / Volts	: 260A / 28V
Shielding Gas	: Ar+20%CO ₂	Stick-Out	: 20~25mm (0.79~0.98in)
Flow Rate	: 20 ℓ /min	Welding Speed	: 30 cm/min (12 in/min)
Welding Position	: 1G (PA)	Current Type & Polarity	: DC(+)

❖ Hydrogen Analysis Using Gas Chromatography Method

Hydrogen Evolution Time	: 72 hrs
Evolution Temp.	: 45 °C (113°F)
Barometric Pressure	: 780 mm-Hg

❖ Result(*ml*/100g Weld Metal)

x1	x2	x3	X4
1.56	1.52	1.49	1.55

Average Hydrogen Content **1.53 *ml* / 100g Weld Metal**



❖ Proper welding parameters

Consumable	Shielding Gas	Item	Wire Dia.	
			1.2mm (0.045in)	1.6mm (1/16in)
SL-61MAG	Ar +20%CO ₂	Amp.(A)	180~280	220~360
		Volt.(V)	22~30	24~36

❖ F No & A No

F No	A No
6	1